

## Durham Research Online

---

### Deposited in DRO:

30 June 2017

### Version of attached file:

Published Version

### Peer-review status of attached file:

Peer-reviewed

### Citation for published item:

Yang, Xiaoping and Wang, Shiqing and King, Tyler L. and Kerr, Christopher J. and Blanchet, Clement and Svergun, Dmitri and Pal, Robert and Beeby, Andrew and Vadivelu, Jamuna and Brown, Katherine A. and Jones, Richard A. and Zhang, Lijie and Huang, Shaoming (2016) 'Anisotropic lanthanide-based nano-clusters for imaging applications.', *Faraday discussions.*, 191 . pp. 465-479.

### Further information on publisher's website:

<https://doi.org/10.1039/c6fd00018e>

### Publisher's copyright statement:

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

### Additional information:

---

### Use policy

The full-text may be used and/or reproduced, and given to third parties in any format or medium, without prior permission or charge, for personal research or study, educational, or not-for-profit purposes provided that:

- a full bibliographic reference is made to the original source
- a [link](#) is made to the metadata record in DRO
- the full-text is not changed in any way

The full-text must not be sold in any format or medium without the formal permission of the copyright holders.

Please consult the [full DRO policy](#) for further details.

## PAPER

View Article Online  
View Journal | View Issue

## Anisotropic lanthanide-based nano-clusters for imaging applications†

Xiaoping Yang,<sup>a</sup> Shiqing Wang,<sup>a</sup> Tyler L. King,<sup>b</sup> Christopher J. Kerr,<sup>c</sup> Clement Blanchet,<sup>c</sup> Dmitri Svergun,<sup>c</sup> Robert Pal,<sup>d</sup> Andrew Beeby,<sup>d</sup> Jamuna Vadivelu,<sup>e</sup> Katherine A. Brown,<sup>\*cf</sup> Richard A. Jones,<sup>\*c</sup> Lijie Zhang<sup>a</sup> and Shaoming Huang<sup>\*a</sup>

Received 18th February 2016, Accepted 31st March 2016

DOI: 10.1039/c6fd00018e

We have developed a new class of lanthanide nano-clusters that self-assemble using flexible Schiff base ligands. Cd–Ln and Ni–Ln clusters,  $[\text{Ln}_8\text{Cd}_{24}(\text{L}^1)_{12}(\text{OAc})_{39}\text{Cl}_7(\text{OH})_2]$  ( $\text{Ln} = \text{Nd}, \text{Eu}$ ),  $[\text{Eu}_8\text{Cd}_{24}(\text{L}^1)_{12}(\text{OAc})_{44}]$ ,  $[\text{Ln}_8\text{Cd}_{24}(\text{L}^2)_{12}(\text{OAc})_{44}]$  ( $\text{Ln} = \text{Nd}, \text{Yb}, \text{Sm}$ ) and  $[\text{Nd}_2\text{Ni}_4(\text{L}^3)_2(\text{acac})_6(\text{NO}_3)_2(\text{OH})_2]$ , were constructed using different types of flexible Schiff base ligands. These molecular nano-clusters exhibit anisotropic architectures that differ considerably depending upon the presence of Cd (nano-drum) or Ni (square-like nano-cluster). Structural characterization of the self-assembled particles has been undertaken using crystallography, transmission electron microscopy and small-angle X-ray scattering. Comparison of the metric dimensions of the nano-drums shows a consistency of size using these techniques, suggesting that these molecules may share similar structural features in both solid and solution states. Photophysical properties were studied by excitation of the ligand-centered absorption bands in the solid state and in solution, and using confocal microscopy of microspheres loaded with the compounds. The emissive properties of these compounds vary depending upon the combination of lanthanide and Cd or Ni present in these clusters. The results provide new insights into the construction of novel high-nuclearity nano-clusters and offer a promising foundation for the development of new functional nanomaterials.

<sup>a</sup>College of Chemistry and Materials Engineering, Wenzhou University, Zhejiang Key Laboratory of Carbon Materials, Wenzhou 325035, China. E-mail: smhuang@wzu.edu.cn; Tel: +86 577 88373064

<sup>b</sup>The University of Texas at Austin, Department of Chemistry, Austin, Texas, 78712, USA. E-mail: rajones@cm.utexas.edu; Tel: +1 512 4711706

<sup>c</sup>European Molecular Biology Laboratory, Hamburg Unit, EMBL c/o DESY, Hamburg, 22607, Germany

<sup>d</sup>Department of Chemistry, University of Durham, South Road, Durham, DH1 3LE, UK

<sup>e</sup>Department of Medical Microbiology, University of Malaya, Kuala Lumpur 50603, Malaysia

<sup>f</sup>Cavendish Laboratory, Department of Physics, University of Cambridge, Cambridge CB3 0HE, UK. E-mail: kb518@cam.ac.uk

† Electronic supplementary information (ESI) available: Characterization details for clusters 1–3. CCDC 1450317–1450319. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c6fd00018e




# Introduction

Lanthanide nanomaterials are being increasingly investigated for applications in bio-imaging and molecular recognition,<sup>1</sup> due in part to their advantageous photophysical properties, which include a very large pseudo-Stokes shift between the excitation and emission wavelengths, the absence of photo-bleaching, long lived excited states and narrow emission bands.<sup>1,2</sup> Since emissions *via* 4f–4f transitions are parity forbidden,<sup>3</sup> Ln<sup>3+</sup> ions usually have a relatively long photoluminescence lifetime of the excited state. This can allow for gated and time-resolved photoluminescence detection and thus can eliminate interference from short-lived autofluorescence.

High-nuclearity heterometallic nano-clusters composed of d-block transition metals and lanthanide ions (Ln) have received extensive attention due not only to their aesthetically stunning molecular structures but also their versatile applications in optoelectronics, magnetism, and as probes in biological systems.<sup>4</sup> Most trivalent lanthanide ions exhibit long-lived (in the microsecond-to-millisecond range) and line-like emission bands at characteristic wavelengths, *e.g.* Tb<sup>3+</sup> (green), Eu<sup>3+</sup> (red) and Yb<sup>3+</sup>, Nd<sup>3+</sup>, and Er<sup>3+</sup> (near infra-red, NIR). These characteristics allow time-gated detection. More specifically, the NIR emitters have some potential applications in bioassays and luminescent probes because of the transparency of biological tissues to electromagnetic radiation in the range of 0.8–1.3  $\mu\text{m}$ .<sup>5</sup> In high-nuclearity d–f clusters, light-absorbing d-block metal chromophores (*i.e.* Pt<sup>II</sup>,<sup>6a,b</sup> Ru<sup>II</sup>,<sup>6c,d</sup> Zn<sup>II</sup>,<sup>6e,f</sup> and Cd<sup>II</sup><sup>6g,h</sup>) can act as sensitizers for luminescence from Ln(III) centers following d  $\rightarrow$  f energy-transfer. Many reports have so far been focused on high-nuclearity 3d–4f clusters, such as Cu/Ln,<sup>7a</sup> Mn/Ln<sup>7b,c</sup> and Ni/Ln<sup>7d,e</sup> cluster systems, in order to study their magnetic properties as single-molecule magnets. In contrast, high-nuclearity 4d–f systems with luminescence properties have received much less attention.

Compartmental Schiff bases with two dissimilar metal-binding sites, one being specific for the d metal ion and another for the f metal ion, have been employed to synthesize d–f heteronuclear clusters.<sup>8</sup> Recent studies in our laboratories have focused on the construction of luminescent d–f clusters with flexible Schiff base ligands.<sup>9</sup> Flexible ligands may provide more possibilities for the construction of unique frameworks because of their freedom of conformation. In our previous studies, the use of Schiff base ligands which have flexible carbon–carbon backbones containing from 2 to 4 methylene (CH<sub>2</sub>) units, resulted in a variety of binuclear,<sup>10a</sup> trinuclear,<sup>10b</sup> tetranuclear,<sup>10c</sup> and hexanuclear<sup>10d,e</sup> 3d–4f complexes (3d = Zn, Cu and Ni). Recently, we discovered a series of 24-metal Cd–Ln complexes [Ln<sub>6</sub>Cd<sub>18</sub>(L<sup>1</sup>)<sub>9</sub>Cl<sub>8</sub>(OAc)<sub>28</sub>] from reactions of a flexible Schiff base ligand, *N,N'*-bis(5-bromo-3-methoxysalicylidene)hexane-1,6-diamine (H<sub>2</sub>L<sup>1</sup>), which has a 6 carbon backbone (Scheme 1), with Cd(OAc)<sub>2</sub>·4H<sub>2</sub>O and LnCl<sub>3</sub>·6H<sub>2</sub>O.<sup>9b</sup> The structures of these metal clusters are often influenced by a variety of factors such as the ligand structure, the nature of the counter anions, and the pH value of the surrounding environment. As part of our continuing studies focused on the construction of luminescent polynuclear lanthanide-based frameworks, we report here seven d–f clusters with H<sub>2</sub>L<sup>1</sup>, H<sub>2</sub>L<sup>2</sup> and long-chain Schiff base ligand *N,N'*-bis(5-bromo-3-methoxysalicylidene) (*N,N'*-(3-amion-propyl)-propane)-1,6-diamine (H<sub>2</sub>L<sup>3</sup>), which has a flexible (CH<sub>2</sub>)<sub>3</sub>NH(CH<sub>2</sub>)<sub>3</sub> backbone



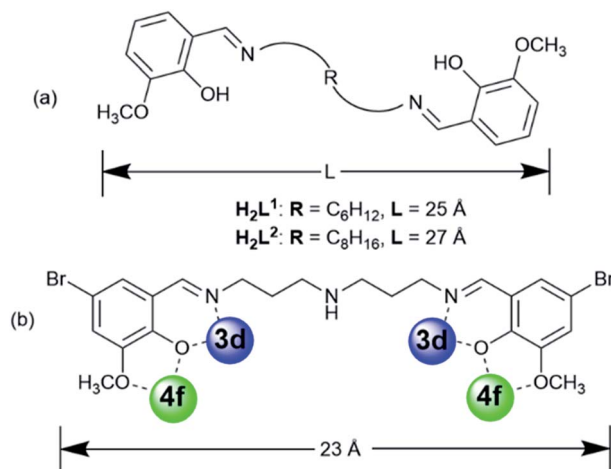

Scheme 1 (a) Flexible Schiff base ligands; (b) the "stretching" coordination mode of  $H_2L^3$ .

(Scheme 1b). They are  $[Ln_8Cd_{24}(L^1)_{12}(OAc)_{39}Cl_7(OH)_2]$  ( $Ln = Nd$  (**1**) and  $Eu$  (**2**)),  $[Nd_2Ni_4(L^3)_2(acac)_6(NO_3)_2(OH)_2]$  (**3**),  $[Ln_8Cd_{24}(L^2)_{12}(OAc)_{48}]$  ( $Ln = Eu$  (**4**) and  $Sm$  (**5**)) and  $[Ln_8Cd_{24}(L^2)_{12}(OAc)_{44}Cl_4]$  ( $Ln = Nd$  (**6**) and  $Yb$  (**7**)). **1** and **2** were synthesized from the reactions of  $H_2L^1$  with  $CdCl_2 \cdot 2H_2O$  and  $Ln(OAc)_3 \cdot 4H_2O$  in the presence of  $NaOH$ . Interestingly, differing from our previously reported  $Cd-Ln$  complexes  $[Ln_6Cd_{18}(L^1)_9Cl_8(OAc)_{28}]$ , **1** and **2** exhibit 32-metal anisotropic nano-drum-like architectures. Hydroxide ( $OH^-$ ) anions are found in the structures of **1** and **2**, indicating that the basic environment favors the formation of these complexes. The structures appear to be ligand and anion dependent. Compared with  $H_2L^1$  and  $H_2L^2$ ,  $H_2L^3$  features a backbone  $NH$  group. Thus, **3** shows a 6-metal square-like structure. The flexible Schiff-base ligands  $H_2L^1$ ,  $H_2L^2$  and  $H_2L^3$  exhibit "stretched" coordination modes with metal ions (Scheme 1b), resulting in the large sizes of **1–7**. For example, the sizes of **1** and **2** are approximately  $19 \times 20 \times 20 \text{ \AA}$ , which are much larger than most other d-f Schiff base polynuclear complexes thus far reported. To further explore the self-assembly properties and imaging of these molecules, we also report preliminary small angle X-ray scattering measurements and confocal imaging of  $Cd-Ln$  complexes containing the  $H_2L^2$  Schiff base ligand.

## Experimental section

### General information

All reactions were performed under dry oxygen-free dinitrogen atmospheres using standard Schlenk techniques. The Schiff-base ligands  $H_2L^{1,2,3}$  were prepared according to well-established procedures.<sup>11</sup> Physical measurements: NMR: VARIAN UNITY-plus 600 spectrometer ( $^1H$ , 600 MHz) at 298 K; IR: Nicolet IR 200 FTIR spectrometer. Elemental analyses (C, H, N) were carried out on a EA1112 elemental analyser. Melting points were obtained in sealed glass capillaries under dinitrogen and are uncorrected. Conductivity measurements were carried out with a DDS-11 conductivity bridge for  $10^{-3} \text{ M}$  solutions in  $CH_3CN$ . Transmission



electron microscopy (TEM) images were recorded on a JEOL JEM-1200EX transmission electron microscope. Scanning electron microscopy (SEM) images were recorded on a Nova NanoSEM 200 scanning electron microscope. Absorption spectra were obtained on a UV-3600 spectrophotometer, and excitation and emission spectra on a QuantaMaster PTI fluorimeter.

## Syntheses

**[Nd<sub>8</sub>Cd<sub>24</sub>(L<sup>1</sup>)<sub>12</sub>(OAc)<sub>39</sub>Cl<sub>7</sub>(OH)<sub>2</sub>] (1).** CdCl<sub>2</sub>·2H<sub>2</sub>O (0.0439 g, 0.20 mmol), Nd(OAc)<sub>3</sub>·4H<sub>2</sub>O (0.0393 g, 0.10 mmol) and H<sub>2</sub>L<sup>1</sup> (0.0770 g, 0.20 mmol) were dissolved in MeOH (20 mL) at room temperature, and a solution of NaOH in EtOH (0.04 mol L<sup>-1</sup>, 10 mL) was then added. The resulting solution was stirred and heated under reflux (30 min). The mixture was allowed to cool and was then filtered. Diethyl ether was allowed to diffuse slowly into the filtrate at room temperature and pale yellow crystals were obtained after one week. The crystals were filtered off, washed with EtOH (5 mL) and dried in the air. Yield (based on CdCl<sub>2</sub>·2H<sub>2</sub>O): 0.0623 g (63%). Mp > 217 °C (dec.). Found: C, 36.55; H, 4.71; N, 2.39%. Calc. for C<sub>342</sub>H<sub>428</sub>Cd<sub>24</sub>Cl<sub>7</sub>Nd<sub>8</sub>N<sub>24</sub>O<sub>128</sub>(EtOH)<sub>6</sub>(EtOEt)<sub>2</sub>(MeOH)<sub>8</sub>(H<sub>2</sub>O)<sub>15</sub>: C, 37.08; H, 4.56; N, 2.81%. IR (CH<sub>3</sub>OH, cm<sup>-1</sup>): 3091 (w), 2935 (w), 1630 (s), 1575 (m), 1472 (m), 1350 (w), 1309 (m), 1239 (m), 1213 (s), 1082 (m), 1045 (m), 962 (w), 847 (m), 795 (s), 672 (w), 616 (w).

**[Eu<sub>8</sub>Cd<sub>24</sub>(L<sup>1</sup>)<sub>12</sub>(OAc)<sub>39</sub>Cl<sub>7</sub>(OH)<sub>2</sub>] (2).** The procedure was the same as that for 1 using Eu(OAc)<sub>3</sub>·4H<sub>2</sub>O (0.0418 g, 0.10 mmol). Pale yellow single crystals of 2 were formed after one week. Yield (based on CdCl<sub>2</sub>·2H<sub>2</sub>O): 0.0519 g (52%). Mp > 220 °C (dec.). Found: C, 36.72; H, 4.57; N, 2.51%. Calc. for C<sub>342</sub>H<sub>428</sub>Cd<sub>24</sub>Cl<sub>7</sub>Eu<sub>8</sub>N<sub>24</sub>O<sub>128</sub>(EtOH)<sub>5</sub>(EtOEt)<sub>2</sub>(MeOH)<sub>6</sub>(H<sub>2</sub>O)<sub>12</sub>: C, 37.00; H, 4.43; N, 2.83%. IR (CH<sub>3</sub>OH, cm<sup>-1</sup>): 3099 (w), 1637 (m), 1578 (s), 1470 (s), 1410 (m), 1341 (m), 1318 (w), 1210 (s), 1088 (m), 1039 (m), 962 (m), 855 (m), 798 (s), 673 (m), 638 (m), 615 (w).

**[Nd<sub>2</sub>Ni<sub>4</sub>(L<sup>3</sup>)<sub>2</sub>(acac)<sub>6</sub>(NO<sub>3</sub>)<sub>2</sub>(OH)<sub>2</sub>] (3).** The procedure was the same as that for 1 using Ni(acac)<sub>2</sub>·2H<sub>2</sub>O (0.1534 g, 0.52 mmol), Nd(NO<sub>3</sub>)<sub>3</sub>·6H<sub>2</sub>O (0.0526 g, 0.12 mmol) and H<sub>2</sub>L<sup>3</sup> (0.26 mmol, 0.1448 g). Pale green single crystals of 3 were formed after two weeks. Yield (based on Nd(NO<sub>3</sub>)<sub>3</sub>·6H<sub>2</sub>O): 0.0756 g (52%). Mp > 178 °C (dec.). Found: C, 26.39; H, 2.13; N, 4.16%. Calc. for C<sub>56</sub>H<sub>50</sub>Br<sub>4</sub>Nd<sub>2</sub>N<sub>8</sub>Ni<sub>4</sub>O<sub>52</sub>: C, 26.86; H, 2.00; N, 4.48%. IR (CH<sub>3</sub>OH, cm<sup>-1</sup>): 2933 (m), 1631 (m), 1575 (s), 1432 (s), 1400 (s), 1301 (m), 1205 (s), 1072 (m), 1022 (w), 970 (w), 845 (w), 730 (s), 666 (m).

**[Eu<sub>8</sub>Cd<sub>24</sub>(L<sup>2</sup>)<sub>12</sub>(OAc)<sub>48</sub>] (4).** Cd(OAc)<sub>2</sub>·2H<sub>2</sub>O (0.1382 g, 0.52 mmol), Eu(OAc)<sub>3</sub>·4H<sub>2</sub>O (0.0502 g, 0.12 mmol) and H<sub>2</sub>L<sup>2</sup> (0.1073 g, 0.26 mmol) were dissolved in MeOH (30 mL) at room temperature and 4 drops of Et<sub>3</sub>N were added. The resulting solution was stirred and heated under reflux for 1 hour. The mixture was then allowed to cool to room temperature and was gravity filtered. Diethyl ether was allowed to diffuse slowly into the filtrate at room temperature and yellow crystals were obtained after one week. The crystals were washed with EtOH (5 mL) and Et<sub>2</sub>O (5 mL) and collected and dried in the air. Yield (based on Eu(OAc)<sub>3</sub>·4H<sub>2</sub>O): 0.0478 g (53%). Mp > 216 °C (dec.). IR (neat, cm<sup>-1</sup>): 2926 (w), 2825 (w), 1630 (m), 1552 (s), 1403 (s), 1345 (m), 1305 (m), 1210 (s), 1167 (m), 1097 (m), 1078 (m), 1017 (w), 964 (w), 852 (w), 735 (s), 666 (m).

**[Sm<sub>8</sub>Cd<sub>24</sub>(L<sup>2</sup>)<sub>12</sub>(OAc)<sub>48</sub>] (5).** The synthesis of 5 was the same as that for 4 using Sm(OAc)<sub>3</sub>·4H<sub>2</sub>O (0.0482 g, 0.12 mmol). Yellow crystals of 5 were formed after one week. Yield (based on Sm(OAc)<sub>3</sub>·4H<sub>2</sub>O): 0.0419 g (47%). Mp > 207 °C (dec.). IR



(CH<sub>3</sub>OH, cm<sup>-1</sup>): 2926 (w), 1631 (m), 1575 (s), 1558 (s), 1471 (m), 1410 (s), 1306 (m), 1212 (s), 1074 (m), 1016 (w), 966 (w), 854 (w), 734 (s), 665 (w).

[Nd<sub>8</sub>Cd<sub>24</sub>(L<sup>2</sup>)<sub>12</sub>(OAc)<sub>44</sub>Cl<sub>4</sub>] (6). The synthesis of 6 was the same as that for 4 using NdCl<sub>3</sub>·6H<sub>2</sub>O (0.0431 g, 0.12 mmol). Yellow crystals were obtained after one week. Yield (based on NdCl<sub>3</sub>·6H<sub>2</sub>O): 0.0712 g (45%). Mp > 209 °C (dec.). IR (CH<sub>3</sub>OH, cm<sup>-1</sup>): 3374 (w), 2930 (w), 1631 (m), 1572 (s), 1470 (m), 1410 (s), 1347 (w), 1307 (m), 1238 (m), 1212 (s), 1080 (m), 1048 (m), 963 (w), 849 (m), 738 (s), 673 (s), 640 (m).

[Yb<sub>8</sub>Cd<sub>24</sub>(L<sup>2</sup>)<sub>12</sub>(OAc)<sub>44</sub>Cl<sub>4</sub>] (7). The synthesis of 7 was the same as that for 4 using YbCl<sub>3</sub>·6H<sub>2</sub>O (0.0466 g, 0.12 mmol). Pale yellow single crystals of 7 were formed after one week. Yield (based on YbCl<sub>3</sub>·6H<sub>2</sub>O): 0.0612 g (37%). Mp > 209 °C (dec.). IR (CH<sub>3</sub>OH, cm<sup>-1</sup>): 2930 (w), 1635 (m), 1576 (s), 1468 (m), 1407 (s), 1340 (w), 1309 (m), 1238 (m), 1212 (s), 1078 (m), 1020 (m), 962 (m), 854 (m), 735 (s), 676 (m), 638 (m).

### X-ray analysis

Data were collected using a Smart APEX CCD diffractometer with graphite monochromated Mo-K $\alpha$  radiation ( $\lambda$  = 0.71073 Å) at 223 K. The data set was corrected for absorption based on multiple scans and reduced using standard methods. Data reduction was performed using DENZO-SMN.<sup>12</sup> The structures were solved by direct methods and refined anisotropically using full-matrix least-squares methods with the SHELX 97 program package.<sup>12</sup> Coordinates of the non-hydrogen atoms were refined anisotropically, while hydrogen atoms were included in the calculation isotropically but not refined. Neutral atom scattering factors were taken from Cromer and Waber.<sup>14</sup>

For the crystal structures of 1 and 2, some uncoordinated solvent molecules such as CH<sub>3</sub>OH, C<sub>2</sub>H<sub>5</sub>OH, C<sub>2</sub>H<sub>5</sub>OC<sub>2</sub>H<sub>5</sub> and H<sub>2</sub>O molecules were found to be badly disordered. Attempts to model the disorder were unsatisfactory. The contributions to the scattering factors due to these solvent molecules were removed by use of the utility SQUEEZE<sup>15a</sup> in PLATON98.<sup>15b,c</sup> PLATON98 was used as incorporated in WinGX.<sup>15d</sup> Crystallographic data for 1–3 (CCDC reference numbers 1450317–1450319) are presented in Table S1 and selected bond lengths are given in Tables S2–S4.†

1: C<sub>342</sub>H<sub>428</sub>Cd<sub>24</sub>Cl<sub>7</sub>N<sub>24</sub>Nd<sub>8</sub>O<sub>128</sub>, orthorhombic, space group *Pna*2(1), *a* = 54.734(11), *b* = 27.619(12), *c* = 35.243(18) Å,  $\alpha$  = 90°,  $\beta$  = 90°,  $\gamma$  = 90°, *V* = 53 277(18) Å<sup>3</sup>, *Z* = 4, *D*<sub>c</sub> = 1.374 g cm<sup>-3</sup>,  $\mu$ (Mo-K $\alpha$ ) = 1.798 mm<sup>-1</sup>, *F*(000) = 21 692, *T* = 223 K. *R*<sub>1</sub> = 0.1018, *wR*<sub>2</sub> = 0.2608 for 90 178 independent reflections with a goodness-of-fit of 1.038.

2: C<sub>342</sub>H<sub>428</sub>Cd<sub>24</sub>Cl<sub>7</sub>N<sub>24</sub>Eu<sub>8</sub>O<sub>128</sub>, orthorhombic, space group *Pna*2(1), *a* = 54.106(11), *b* = 27.127(5), *c* = 34.876(7) Å,  $\alpha$  = 90°,  $\beta$  = 90°,  $\gamma$  = 90°, *V* = 51 189(18) Å<sup>3</sup>, *Z* = 4, *D*<sub>c</sub> = 1.438 g cm<sup>-3</sup>,  $\mu$ (Mo-K $\alpha$ ) = 2.040 mm<sup>-1</sup>, *F*(000) = 21 788, *T* = 223 K. *R*<sub>1</sub> = 0.1035, *wR*<sub>2</sub> = 0.2090 for 86 518 independent reflections with a goodness-of-fit of 0.922.

3: C<sub>56</sub>H<sub>50</sub>Br<sub>4</sub>N<sub>8</sub>Nd<sub>2</sub>Ni<sub>4</sub>O<sub>52</sub>, monoclinic, space group *P*2<sub>1</sub>/*c*, *a* = 15.462(3), *b* = 19.156(4), *c* = 19.871(4) Å,  $\alpha$  = 90°,  $\beta$  = 107.63°(3),  $\gamma$  = 90°, *V* = 5609.2(19) Å<sup>3</sup>, *Z* = 2, *D*<sub>c</sub> = 1.481 g cm<sup>-3</sup>,  $\mu$ (Mo-K $\alpha$ ) = 3.073 mm<sup>-1</sup>, *F*(000) = 2452, *T* = 223 K. *R*<sub>1</sub> = 0.0781, *wR*<sub>2</sub> = 0.2092 for 9806 independent reflections with a goodness-of-fit of 1.061.



## Small-angle X-ray scattering (SAXS)

SAXS data for  $[\text{Eu}_8\text{Cd}_{24}(\text{L}^2)_{12}(\text{OAc})_{48}]$  (**4**) were collected on the SAXS beamline P12 at the PETRA III storage ring (Deutsches Elektronen-Synchrotron, Hamburg).<sup>13</sup> Using a PILATUS 2M pixel detector at a sample-detector distance of 3.0 m and at an energy of 9.7 keV ( $\lambda = 1.28 \text{ \AA}$ ), the range of momentum transfer  $0.01 < s < 0.45 \text{ \AA}^{-1}$  was covered ( $s = 4\pi \sin \theta/\lambda$ , where  $2\theta$  is the scattering angle). Solute concentrations of 1.8 and  $3.7 \text{ mg mL}^{-1}$  were measured in MeOH/MeCN (50 : 50) at  $20^\circ\text{C}$ . Samples were loaded manually into the observation capillary. Primary data processing steps were performed using the automated data pipeline SASFLOW.<sup>16</sup>

## Polystyrene bead loading

Luminex MicroPlex microspheres ( $6 \mu\text{m}$  cross-linked polystyrene beads with surface carboxyl groups) were prepared for loading by drying  $12.5 \times 10^6$  beads under high vacuum for 24 hours. The dried beads were resuspended in a chloroform/MeOH solution (1 mL, 50 : 50) containing 5 mg of sample. This suspension was rotated slowly for 2 days. The suspension was then centrifuged, the supernatant discarded and the beads washed with MeOH ( $3 \times 1 \text{ mL}$ ) followed by drying under high vacuum (24 h).

## Confocal microscopy of polystyrene beads

Images were recorded using a Leica SP5 II confocal microscope equipped with a HCX PL APO 63x/1.40 NA LambdaBlue Oil immersion objective. Data were collected using  $5\times$  digital magnification at a 400 Hz/line scan speed (4 line average, bidirectional scanning) at 355 nm ( $3^{\text{rd}}$  harmonic NdYAG laser) with 3 mW laser power. In order to achieve excitation with maximal probe emission, the microscope was equipped with a triple channel imaging detector, comprising two conventional PMT systems and a HyD hybrid avalanche photodiode detector. The latter part of the detection system, when operated in the BrightRed mode, is capable of improving imaging sensitivity by 25%, reducing signal to noise by a factor of 5. Frame size was determined at  $2048 \times 2048$  pixels, with a 0.6 airy disc unit determining the applied pinhole diameter rendering one voxel to correspond to  $24.02 \times 24.02 \text{ nm}$  (frame size  $49.16 \times 49.16 \mu\text{m}$ ) with a section thickness of 380 nm. This particular LSCM is equipped with a novel structural illumination module called PhMoNa (achievable resolution  $62 \times 62 \times 280 \text{ nm}$ ).<sup>17</sup> To detect sensitized Ln emission, a corresponding detection window of 400–800 nm was used to record images using only the above detailed 355 nm laser line.

## Results and discussion

In the presence of NaOH ( $0.01 \text{ mol L}^{-1}$ ), reactions of  $\text{H}_2\text{L}^1$  with  $\text{CdCl}_2 \cdot 2\text{H}_2\text{O}$  and  $\text{Ln}(\text{OAc})_3 \cdot 4\text{H}_2\text{O}$  in refluxing methanol/ethanol produced yellow solutions from which **1** and **2** were isolated as pale yellow crystalline solids. **1** and **2** are isomorphous and have 32-metal drum-like structures. Two views of the crystal structure of **1** are shown in Fig. 1a. The top view is essentially a side-on view while the lower one is looking down into the top of the drum. The ends of the drum are created by two rings of 16 metals (4 Nd(III) and 12 Cd(II)) coordinated to half of the N, O binding groups of the 12 Schiff base ligands. The sides of the drum are





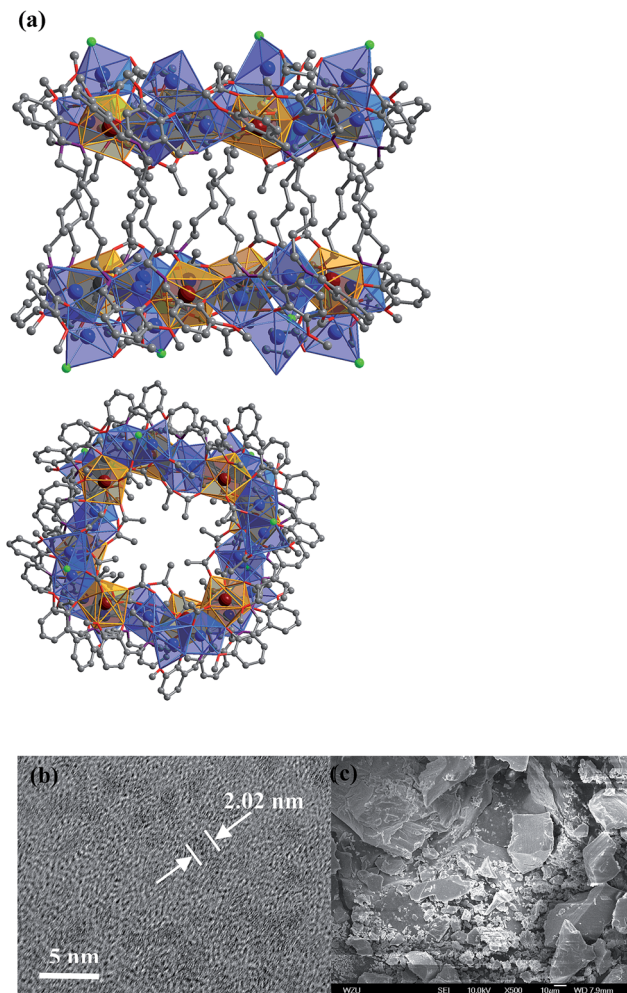


Fig. 1 (a) Two views of the nano-drum-like structure of **1**: viewed along the *b*-axis (top) and the *ac*-axis (lower) ( $\text{Nd}^{3+}$ : brown;  $\text{Cd}^{2+}$ : blue;  $\text{Cl}^-$ : green); (b and c) TEM and SEM images of **1**.

formed by the  $-(\text{CH}_2)_6-$  linkers of the Schiff base ligands. Regarding the two  $\text{Nd}_4\text{Cd}_{12}$  rings, one includes four  $\text{Cl}^-$ , one  $\text{OH}^-$  and nineteen  $\text{OAc}^-$  anions and the other has three  $\text{Cl}^-$ , one  $\text{OH}^-$  and twenty  $\text{OAc}^-$  anions to balance the charge of the cluster. In **1**, the  $\text{Cd}-\text{O}$  and  $\text{Cd}-\text{N}$  bond lengths range from 2.163 Å to 2.646 Å and 2.210 Å to 2.406 Å, respectively. The  $\text{Nd}-\text{O}$  and  $\text{Nd}-\text{N}$  bond lengths range from 2.208 Å to 2.652 Å and 2.527 Å to 2.650 Å, respectively. In **1** and **2**, each  $\text{Ln}^{3+}$  ion and its closest two  $\text{Cd}^{2+}$  ions are linked by phenolic oxygen atoms of the  $\text{L}^1$  ligand and  $\text{OAc}^-$  anions.

The  $\text{Cd}(\text{II})$  ion tends to have relatively high coordination numbers (6–8) and exhibits variable coordination geometries, somewhat similar to  $\text{Ln}(\text{III})$ . This geometry may favor the formation of high-nuclearity  $\text{Cd}-\text{Ln}$  clusters **1** and **2**. Compared with  $\text{Cd}(\text{II})$ , the  $\text{Ni}(\text{II})$  ion tends to have lower coordination numbers





(4–6) and exhibits some common coordination geometries such as square-planar, tetragonal pyramid and octahedral. Thus, the reaction of  $\text{H}_2\text{L}^3$  with  $\text{Ni}(\text{acac})_2 \cdot 2\text{H}_2\text{O}$  and  $\text{Nd}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$  under the same experimental conditions as above produced green solutions from which **3** was isolated as a green crystalline solid. Two views of the square-like structure of **3** are shown in Fig. 2. The top view is looking down into the top of the rectangle while the lower view is essentially a side-on view. The X-ray structure of **3** reveals a centrosymmetric core with two equivalent  $\text{NdNi}_2(\text{acac})_3(\text{NO}_3)(\text{OH})$  moieties linked by two  $\text{L}^2$  ligands. In each  $\text{NdNi}_2(\text{acac})_3(\text{NO}_3)(\text{OH})$  moiety, the  $\text{Nd}^{3+}$  ion is 8-coordinate, surrounded by eight oxygen atoms from two  $\text{L}^2$  ligands, one  $\text{acac}^-$ , one  $\text{NO}_3^-$  and one  $\text{OH}^-$  ion. Both  $\text{Ni}^{2+}$  ions have bi-pyramidal geometries. They are bridged by one  $\text{acac}^-$  and one  $\text{OH}^-$  ion with a separation of 3.237 Å. The  $\text{Nd}^{3+}$  ion and two  $\text{Ni}^{2+}$  ions are linked by phenolic oxygen atoms of the  $\text{L}^2$  ligand and  $\text{OH}^-$  anions. The average distance between the  $\text{Nd}^{3+}$  and  $\text{Ni}^{2+}$  ions is 3.413 Å.

It is noticeable that the Schiff base ligands exhibit a “stretched” coordination mode with metal ions in **1–3** (Scheme 1b). This may be due to the fact that, compared with those Schiff base ligands with shorter carbon-carbon backbones, there is less of a chelating or templating effect.<sup>1,2</sup> Thus the heights of the drum-like and square-like structures are mainly decided by the lengths of the Schiff base ligands, resulting in the formation of nanoscale clusters. The molecular dimensions of **1** and **2** are bigger than those of **3** (*i.e.*  $19 \times 20 \times 20$  Å for **1** vs.  $8 \times 12 \times 18$  Å for **3**). It is also possible to obtain images of these Cd–Ln molecular nanoparticles using transmission electron microscopy (TEM). Dilute solutions of **1** in  $\text{CH}_3\text{CN}$  were contacted with a Cu grid and the solvent was carefully evaporated under vacuum. The TEM images obtained (Fig. 1b) show uniform nanoparticles with diameters measuring approximately 2.02 nm which corresponds well with the diameter of the 16-metal ring end of the drum found in the crystal structure, indicating that the nano-cluster retains its unique molecular structure in

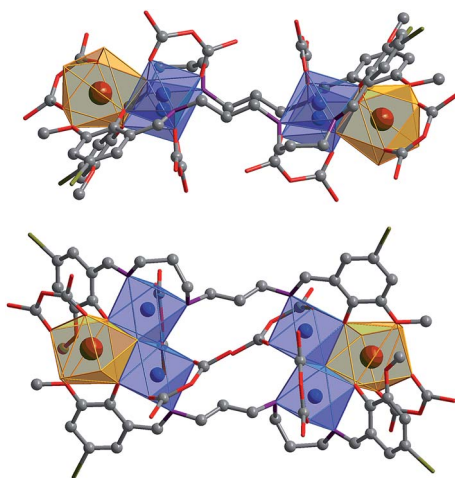


Fig. 2 Two views of the square-like structure of **3**: viewed along the *ac*-axis (top) and the *b*-axis (lower) ( $\text{Nd}^{3+}$ : brown;  $\text{Ni}^{2+}$ : blue).



solution. In Fig. 1c a panoramic scanning electron microscopy (SEM) image shows the crystalline nature of **1**.

The nature of **1** in solution has been probed using molar conductivity and  $^1\text{H}$  NMR studies. Molar conductivity studies of **1** in  $\text{CH}_3\text{CN}$  also confirm that this molecular nanoparticle is neutral in solution, in accordance with the solid state structure. The  $^1\text{H}$  NMR spectrum of **1** in  $\text{CDCl}_3$  contains multiple broad peaks ranging from  $-17$  to  $+18$  ppm, due to the paramagnetic  $\text{Nd}^{3+}$  ion. The  $^1\text{H}$  NMR spectrum of **1** remains unchanged for several weeks, indicating that it is stable in solution (Fig. S1†).

The nature of **4** in solution has been probed using small-angle X-ray scattering (SAXS). SAXS data were obtained at  $1.8$  and  $3.7 \text{ mg mL}^{-1}$ , as described above, and merged using the ALMERGE<sup>18</sup> software as shown in Fig. 3a. Bragg peaks in the scattering data appear to be arising from undissolved material still in a crystalline state. Evaluation of the particle distance distribution function  $P(r)$  was undertaken using GNOM<sup>19</sup> and shows a bi-modal distribution, with a maximum particle dimension of approximately  $2.7 \text{ nm}$ , consistent with the crystal structure of this nano-drum.<sup>20</sup> However, further studies are required to establish conditions that

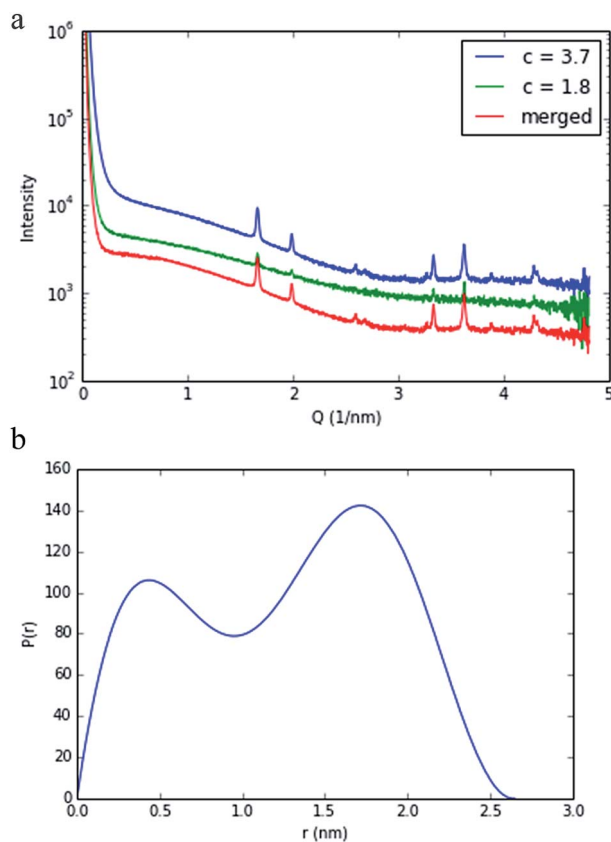


Fig. 3 SAXS analysis of compound **4**. (a) SAXS curves of data collected at  $1.8$  and  $3.7 \text{ mg mL}^{-1}$  are shown with the merged curve that was used as an input to derive (b) the particle distance function,  $P(r)$ , plot.



are purely monodisperse, without the presence of undissolved crystalline material and/or nano-cluster substructures.

The photophysical properties of **1–3** were studied in both solution and the solid state. The d–f clusters' absorption bands in the UV-vis region are all red-shifted compared to those of the ligands alone ( $\text{H}_2\text{L}^{1,2}$ ) (Fig. 4). For the free ligands,  $\text{H}_2\text{L}^{1,2}$ , excitations produce broad emission bands at  $\lambda_{\text{max}} = 515$  nm and 509 nm, respectively (Fig. S2†). The emission and excitation spectra of **1–3** in  $\text{CH}_3\text{CN}$  are shown in Fig. 5, 6 and S3.† Upon excitation of the ligand-centered absorption bands, **1** and **3** show the NIR luminescence of  $\text{Nd}^{3+}$  ( $^4\text{F}_{3/2} \rightarrow ^4\text{I}_{j/2}$  transitions,  $j = 9, 11$  and  $13$ ). As shown in Fig. 6, the emissions at 873 nm can be assigned to the  $^4\text{F}_{3/2} \rightarrow ^4\text{I}_{9/2}$  transition, 1063 nm to the  $^4\text{F}_{3/2} \rightarrow ^4\text{I}_{11/2}$  transition and 1350 nm to the  $^4\text{F}_{3/2} \rightarrow ^4\text{I}_{13/2}$  transition of  $\text{Nd}^{3+}$ . The free Schiff base ligands  $\text{H}_2\text{L}^{1,2}$  and  $\text{Nd}(\text{OAc})_3 \cdot 4\text{H}_2\text{O}$  do not exhibit NIR luminescence in  $\text{CH}_3\text{CN}$  under similar conditions. Upon excitation of the ligand centered absorption bands, **2** shows typical visible emission bands of the  $\text{Eu}^{3+}$  ion ( $^5\text{D}_0 \rightarrow ^7\text{F}_j$  transitions,  $j = 0, 1, 2, 3$  and  $4$ ). As shown in Fig. 5, the appearance of the symmetry-forbidden emission  $^5\text{D}_0 \rightarrow ^7\text{F}_0$  at 579 nm indicates that the  $\text{Eu}^{3+}$  ions in **2** occupy sites with low symmetry and have no inversion center.<sup>21</sup>

This is further confirmed by the intensity ratio of 3.9 for  $I(^5\text{D}_0 \rightarrow ^7\text{F}_2)/I(^5\text{D}_0 \rightarrow ^7\text{F}_1)$ , which is a good measure of the nature and symmetry of the first coordination sphere of the  $\text{Eu}^{3+}$  ion.<sup>22</sup> The overall quantum yield of **2** in  $\text{CH}_3\text{CN}$  was determined as 0.083 relative to  $[\text{Ru}(\text{bipy})_3]\text{Cl}_2$  in water (bipy = 2,2'-bipyridine;  $\Phi_{\text{em}} = 0.028$ )<sup>23</sup> and corrected for the refractive index of the solvent. **1** and **2** show two excitation bands at approximately 280 nm and 350 nm, while **3** has one at approximately 360 nm, in agreement with their absorption spectra, confirming that the energy transfers from the ligand centers to  $\text{Ln}^{3+}$  ions occur (Scheme 2). For each Cd–Ln or Ni–Nd nano-cluster the luminescence spectrum in the solid state is similar to that in solution.

For the Nd(III) nano-clusters **1** and **3**, we were naturally interested in the influence of their structures and d metals on their photophysical properties. The relative emission intensities of **1** and **3** were determined under the same

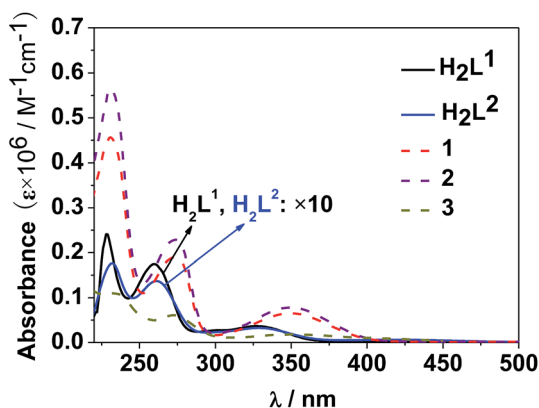


Fig. 4 UV-vis spectra of the free ligands  $\text{H}_2\text{L}^{1,2}$  and clusters **1–3** in  $\text{CH}_3\text{CN}$  ( $C = 10^{-8}$  to  $10^{-7}$  M).



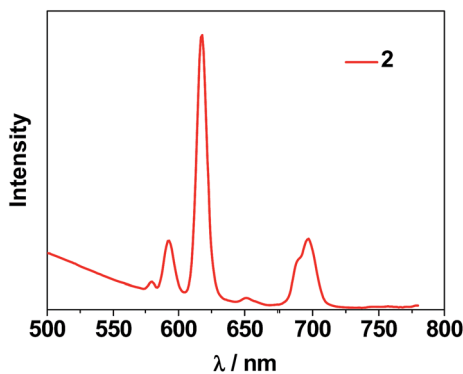


Fig. 5 The visible emission spectrum of **2** in CH<sub>3</sub>CN.

experimental conditions. With the same absorbance value at 355 nm, the relative emission intensity at 1068 nm was estimated to be 5.4 for **1** : **3** in CH<sub>3</sub>CN (Fig. 6), indicating that with the central metal ions encapsulated by chromophoric Cd/L<sup>1</sup> components (energy transfer donors), **1** has superior luminescence properties compared to **3**. It is also noticeable that, compared to the “enclosed” nano-drum-like structure in **1** the “open” square-like structure of **3** results in metal centers which are less well shielded from outside solvents which may quench lanthanide luminescence.<sup>24</sup> In addition, the d-block metal ions introduced into the lanthanide-based clusters may play different roles in the luminescence properties of the Ln<sup>3+</sup> ions. For the Cd<sup>2+</sup> ion, its saturated d<sup>10</sup> electronic configuration prevents the quenching of lanthanide luminescence through a d–d transition (f → d energy transfer), while the Ni<sup>2+</sup> ion may quench the luminescence *via* f → d energy transfer.<sup>25</sup> The emission lifetimes (τ) of **1** and **3** are 1.9 μs and 0.5 μs, respectively. The intrinsic quantum yields (Φ<sub>Ln</sub>) of Nd<sup>3+</sup> emission in **1** and **3** are calculated as 0.76% and 0.20%, respectively, using Φ<sub>Ln</sub> = τ/τ<sub>0</sub> (τ<sub>0</sub> = 250 μs, the natural lifetime of Nd<sup>3+</sup>).<sup>26</sup>

To explore the imaging utility of Cd–Ln nano-clusters on an imaging platform used for biological materials, cross-linked polystyrene beads (6–7 μm) containing


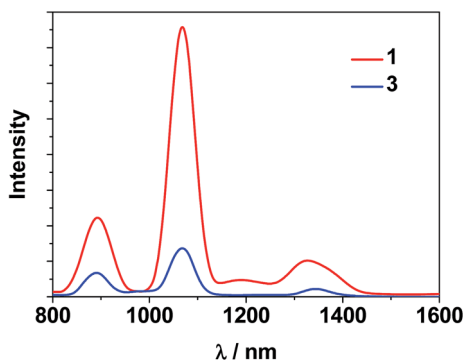


Fig. 6 NIR emission spectra of clusters **1** and **3** with the same absorbance value at λ<sub>ex</sub> = 355 nm in CH<sub>3</sub>CN.



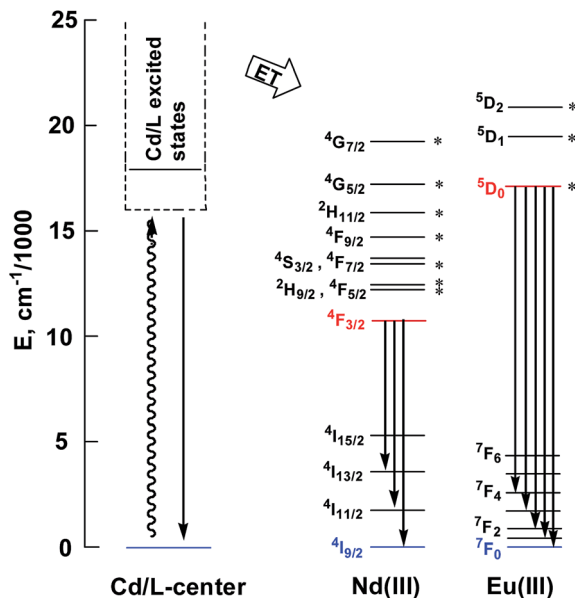

Scheme 2 Relevant energy levels in 1–3. Those marked with \* can act as energy acceptors by either Förster or Dexter mechanisms (the former requiring  $|\Delta J| = 2, 4, \text{ or } 6$  at the lanthanide, and the latter requiring  $|\Delta J| = 0$  or 1 with the exception of  $|\Delta J| = |\Delta J'| = 0$ , which is forbidden).<sup>27</sup>

complexes 5, 6 and 7 were visualized using confocal microscopy (Fig. 7). Images were collected to show total emission (400–800 nm). All experimental parameters are identical and bead emissions shown are a true representation of brightness on a color scale of black to red to white to blue, where blue indicates saturation. As shown in Fig. 7, beads loaded with 5 are considerably brighter, suggesting that the Nd–Cd nano-cluster may have enhanced emission properties with the  $\text{H}_2\text{L}^2$  Schiff base ligand, compared to the Sm–Cd and Yb–Cd nano-clusters. Further analysis of the relative emission intensities between the bead sets can be undertaken to improve the confidence of this observation.

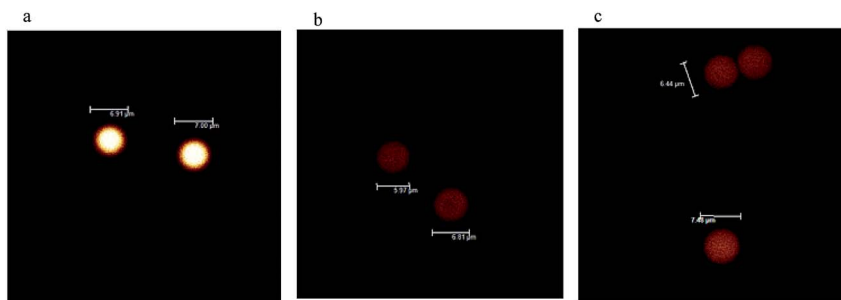


Fig. 7 Confocal images of polystyrene beads loaded with Ln–Cd nano-clusters (a) 5, Nd; (b) 6, Sm, and (c) 7, Yb.



## Conclusions

Nanostructured materials are increasingly being developed as imaging agents for both fundamental research imaging and diagnostic imaging. Here, we have presented data characterizing a new class of self-assembling lanthanide nano-clusters. These compounds have structures and imaging properties making them suitable candidates for cell and deep tissue imaging agents. Unlike classical nanoparticles, these materials are self-assembling homogeneous particles with asymmetric structures. The Cd–Ln clusters adopt nano-drum-like structures. The Ni–Ln cluster **3** has a square-like architecture. TEM and SAXS data are consistent with these molecular compounds having solution structures similar to those found in the solid state. The different architectures give rise to different imaging properties. With the Ln(III) centers enclosed within its nano-drum-like structure, Cd–Nd cluster **1** exhibits better NIR luminescence properties than Ni–Nd cluster **3**. The photophysical properties of the nano-drum-like clusters demonstrate their potential as lanthanide emitters, and their utility as bio-imaging agents in confocal microscopy platforms. Future studies will focus on understanding how their molecular structures influence their stability, photophysical properties and ability to be delivered to cells and tissues in nano-formulations.

## Acknowledgements

The work was supported by the Welch Foundation (F-816) (RAJ), NSFC (51025207) (SMH), the Ministry of High Education (MOHE), Malaysia under High Impact Research (HIR) – MOHE project (UM.C/625/1/HIR/MoE/CHAN/13/6 H-50001-00-A000034) (KAB), NIH/NIAID 1U01AI078008-3, the Centre for Blast Injury Study at Imperial College London (KAB), the Royal Society (University Research Fellowship to RP), and the EU infrastructure grant BioStruct-X (contract number: 283570) (DIS).

## Notes and references

- (a) Y. Sun, W. Feng, P.-Y. Yang, C.-H. Huang and F.-Y. Li, *Chem. Soc. Rev.*, 2015, **44**, 1509–1525; (b) L. Prodi, E. Rampazzo, F. Rastrelli, A. Speghini and N. Zaccheroni, *Chem. Soc. Rev.*, 2015, **44**, 4922–4952; (c) S. Ranjan, M. K. Jayakumar and Y. Zhang, *Nanomedicine*, 2015, **10**, 1477–1491; (d) Q. Liu, W. Feng and F.-Y. Li, *Coord. Chem. Rev.*, 2014, **273/274**, 100–110; (e) A. Foucault-Collet, C. M. Shade, I. Nazarenko, S. Petoud and S. V. Eliseeva, *Angew. Chem., Int. Ed.*, 2014, **53**, 2927–2930.
- (a) E. G. Moore, A. P. S. Samuel and K. N. Raymond, *Acc. Chem. Res.*, 2009, **42**, 542–552; (b) J.-C. G. Bünzli, *Chem. Rev.*, 2010, **110**, 2729–2755; (c) C. P. Montgomery, B. S. Murray, E. J. New, R. Pal and D. Parker, *Acc. Chem. Res.*, 2009, **42**, 925–937; (d) A. Thibon and V. C. Pierre, *Anal. Bioanal. Chem.*, 2009, **394**, 107–120.
- T. Nishioka, K. Fukui and K. Matsumoto, *Handbook on the Physics and Chemistry of Rare Earth*, ed. K. A. Gschneidner, J.-C. G. Bünzli and V. K. Pecharsky, Elsevier Science B. V., Amsterdam, 2007, p. 37.
- (a) J.-B. Peng, Q.-C. Zhang, X.-J. Kong, Y.-Z. Zheng, Y.-P. Ren, L.-S. Long, R.-B. Huang, L.-S. Zheng and Z. Zheng, *J. Am. Chem. Soc.*, 2012, **134**, 3314–3317; (b) B. Wang, Z. Zang, H. Wang, W. Dou, X. Tang, W. Liu, Y. Shao,



- J. Ma, Y. Li and J. Zhou, *Angew. Chem., Int. Ed.*, 2013, **52**, 3756–3759; (c) A. Müller, *Nature*, 2007, **447**, 1034–1035; (d) A. Müller, P. Kögerler and A. W. M. Dress, *Coord. Chem. Rev.*, 2001, **222**, 193–218; (e) E. G. Mednikov, M. C. Jewell and L. F. Dahl, *J. Am. Chem. Soc.*, 2007, **129**, 11619–11630.
- 5 (a) J.-C. G. Bünzli, *Metal Ions in Biological Systems*, ed. M. Dekker, New-York, 2004, p. 42; (b) I. Hemmila and S. Webb, *Drug Discovery Today*, 1997, **2**, 373–380; (c) J. W. Stouwdam, G. A. Hebbink, J. Huskens and F. C. J. M. Van Veggel, *Chem. Mater.*, 2003, **15**, 4604–4616.
- 6 (a) X.-L. Li, L.-X. Shi, L.-Y. Zhang, H. M. Wen and Z. N. Chen, *Inorg. Chem.*, 2007, **46**, 10892–10900; (b) H.-B. Xu, L.-X. Shi, E. Ma, L.-Y. Zhang, Q.-H. Wei and Z.-N. Chen, *Chem. Commun.*, 2006, 1601–1603; (c) H.-M. Wen, Y. Yang, X.-S. Zhou, J.-Y. Liu, D.-B. Zhang, Z.-B. Chen, J.-Y. Wang, Z.-N. Chen and Z.-Q. Tian, *Chem. Sci.*, 2013, **4**, 2471–2477; (d) S. G. Baca, H. Adams, C. S. Grange, A. P. Smith, I. Sazanovich and M. D. Ward, *Inorg. Chem.*, 2007, **46**, 9779–9789; (e) M. Yin, X. Lei, M. Li, L. Yuan and J. Sun, *J. Phys. Chem. Solids*, 2006, **67**, 1372–1378; (f) H.-B. Xu, H.-M. Wen, Z.-H. Chen, J. Li, L.-X. Shi and Z.-N. Chen, *J. Chem. Soc., Dalton Trans.*, 2010, **39**, 1948–1953; (g) Y.-X. Chi, S.-Y. Niu, J. Jin, R. Wang and Y. Li, *J. Chem. Soc., Dalton Trans.*, 2009, **47**, 7653–7659; (h) Y.-X. Chi, S.-Y. Niu, Z.-L. Wang and J. Jin, *Eur. J. Inorg. Chem.*, 2008, 2336–2343.
- 7 (a) S.-C. Xiang, S.-M. Hu, T.-L. Sheng, R.-B. Fu, X.-T. Wu and X.-D. Zhang, *J. Am. Chem. Soc.*, 2007, **129**, 15144–15146; (b) C. M. Zaleski, E. C. Depperman, J. W. Kampf, M. L. Kirk and V. L. Pecoraro, *Angew. Chem., Int. Ed.*, 2004, **43**, 3912–3914; (c) V. M. Mereacre, A. M. Ako, R. Clerac, W. Wernsdorfer, G. Filoti, J. Bartolome, C. E. Anson and A. K. Powell, *J. Am. Chem. Soc.*, 2007, **129**, 9248–9249; (d) X.-J. Kong, Y.-P. Ren, L.-S. Long, Z. Zheng, R.-B. Huang and L.-S. Zheng, *J. Am. Chem. Soc.*, 2007, **129**, 7016–7017; (e) J.-B. Peng, Q.-C. Zhang, X.-J. Kong, Y.-Z. Zheng, Y.-P. Ren, L.-S. Long, R.-B. Huang, L.-S. Zheng and Z.-P. Zheng, *J. Am. Chem. Soc.*, 2012, **134**, 3314–3317.
- 8 (a) M. Sakamoto, K. Manseki and H. Okawa, *Coord. Chem. Rev.*, 2001, **219**, 379–414; (b) R. E. P. Winpenny, *Chem. Soc. Rev.*, 1998, **27**, 447–452; (c) C. Camp, V. Guidal, B. Biswas, J. Pecaut, L. Dubois and M. Mazzanti, *Chem. Sci.*, 2012, **3**, 2433–2448; (d) M. Andruh, *Chem. Commun.*, 2011, **47**, 3025–3042; (e) X. Feng, W. Zhou, Y. Li, H. Ke, J. Tang, R. Clerac, Y. Wang, Z. Su and E. Wang, *Inorg. Chem.*, 2012, **51**, 2722–2724; (f) T. Yamaguchi, J.-P. Costes, Y. Kishima, M. Kojima, Y. Sunatsuki, N. Breffuel, J.-P. Tuchagues, L. Vendier and W. Wernsdorfer, *Inorg. Chem.*, 2010, **49**, 9125–9135.
- 9 (a) X.-P. Yang, R. A. Jones and S.-M. Huang, *Coord. Chem. Rev.*, 2014, **273**, 63–75; (b) X.-P. Yang, D. Schipper, R. A. Jones, L. A. Lytwak, B. J. Holliday and S.-M. Huang, *J. Am. Chem. Soc.*, 2013, **135**, 8468–8471.
- 10 (a) W.-K. Lo, W.-K. Wong, W.-Y. Wong, J. Guo, K.-T. Yeung, Y.-K. Cheng, X.-P. Yang and R. A. Jones, *Inorg. Chem.*, 2006, 9315–9325; (b) X.-P. Yang, S. Desmond, A. Liao, J. M. Stanley, R. A. Jones and B. J. Holliday, *Polyhedron*, 2013, **52**, 165–168; (c) X.-P. Yang, R. A. Jones, V. Lynch, M. M. Oye and A. L. Holmes, *J. Chem. Soc., Dalton Trans.*, 2005, **5**, 849–851; (d) X.-P. Yang, R. A. Jones, W.-K. Wong, V. Lynch, M. M. Oye and A. L. Holmes, *Chem. Commun.*, 2006, 1836–1838; (e) X.-P. Yang, C. Chan, D. Lam, D. Schipper, J. M. Stanley, X. Chen, R. A. Jones, B. J. Holliday, W.-K. Wong, S.-C. Chen and Q. Chen, *J. Chem. Soc., Dalton Trans.*, 2012, **41**, 11449–11453.





- 11 F. Lam, J.-X. Xu and K.-S. Chan, *J. Org. Chem.*, 1996, **61**, 8414–8418.
- 12 Z. Otwinowski and W. Minor, *Methods in Enzymology*, 276: *Macromolecular Crystallography, Part a*, ed. C. W. J. Carter, M. I. Simon and R. M. Sweet, Academic Press, 1997, pp. 307–326, DENZO-SMN.
- 13 G. H. Sheldrick, *SHELX 97, a Software Package for the Solution and Refinement of X-ray Data*, University of Göttingen, Göttingen, Germany, 1997.
- 14 D. T. Cromer and J. T. Waber, *International Tables for X-Ray Crystallography*, Kynoch Press, Birmingham, 1974, vol. 4, Table 2.2A.
- 15 (a) P. van der Sluis and A. L. Spec, *Acta Crystallogr., Sect. A: Found. Crystallogr.*, 1990, **46**, 194–201; (b) A. L. Spec, *Platon, A Multipurpose Crystallographic Tool*, Utrecht, the Netherlands, 1998; (c) A. L. Spec, *J. Appl. Crystallogr.*, 2003, **36**, 7–13; (d) L. J. Farrugia, *J. Appl. Crystallogr.*, 1999, **32**, 837–838.
- 16 D. Franke, A. G. Kikhney and D. I. Svergun, *Nucl. Instrum. Methods Phys. Res., Sect. A*, 2012, **689**, 52–59.
- 17 R. Pal, *Faraday Discuss.*, 2015, **177**, 507–515.
- 18 M. V. Petoukhov, D. Franke, A. V. Shkumatov, G. Tria, A. G. Kikhney, M. Gajda, C. Gorba, H. D. Mertens, P. V. Konarev and D. I. Svergun, *J. Appl. Crystallogr.*, 2012, **45**(2), 342–350.
- 19 D. I. Svergun, *J. Appl. Crystallogr.*, 1992, **25**, 495–503.
- 20 K. A. Brown, X. Yang, D. Schipper, J. W. Hall, L. J. DePue, A. J. Gnanam, J. F. Arambula, J. N. Jones, J. Swaminathan, Y. Dieye, J. Vadivelu, D. J. Chandler, E. M. Marcotte, J. L. Sessler, L. I. R. Ehrlich and R. A. Jones, *Dalton Trans.*, 2015, **44**, 2667–2675.
- 21 (a) D. H. Metcalf, R. G. Ghirardelli and R. A. Palmer, *Inorg. Chem.*, 1985, **24**, 634–636; (b) M. Albin, R. R. Whittle and W. D. Horrocks Jr, *Inorg. Chem.*, 1985, **24**, 4591–4594.
- 22 (a) Q. H. Xu, L. S. Li, X. S. Liu and R. R. Xu, *Chem. Mater.*, 2002, **14**, 549–555; (b) J.-C. G. Bünzli and C. Piguet, *Chem. Soc. Rev.*, 2005, **34**, 1048–1077; (c) Y. B. Katsimirski and N. K. Davidenko, *Coord. Chem. Rev.*, 1979, **27**, 223–273.
- 23 K. Nakamaru, *Bull. Chem. Soc. Jpn.*, 1982, **5**, 2697–2705.
- 24 (a) F. S. Richardson, *Chem. Rev.*, 1982, **82**, 541–552; (b) S. Yanagida, Y. Hasegawa, K. Murakoshi, Y. Wada, N. Nakashima and T. Yamanaka, *Coord. Chem. Rev.*, 1998, **171**, 461–480.
- 25 (a) V. Wen, Y. Zhao, L. Wang, M. Zhang and D. Gao, *J. Rare Earths*, 2007, **25**, 679–683; (b) E. Wolcan, L. Villata, A. L. Capparelli and M. R. Feliz, *Photochem. Photobiol. Sci.*, 2004, **3**, 322–328; (c) B. C. Barja, A. Remorino, M. J. Roberti and P. F. Aramendia, *J. Argent. Chem. Soc.*, 2005, **93**, 81–88; (d) Q.-Y. Chen, C.-J. Li and Q.-H. Luo, *Synth. React. Inorg. Met.-Org. Chem.*, 2003, **33**(9), 1701–1715.
- 26 (a) S. B. Meshkova, Z. M. Topilova, D. V. Bolshoy, S. V. Beltyukova, M. P. Tsvirko, V. Y. Venchikov and V. Ya, *Acta Phys. Pol., A*, 1999, **95**, 983–990; (b) S. I. Klink, L. Grave, D. N. Reinhoudt and F. C. J. M. v. Veggel, *J. Phys. Chem. A*, 2000, **104**, 5457–5468.
- 27 (a) D. L. Dexter, *J. Chem. Phys.*, 1953, **21**, 836–850; (b) G. F. de Sá, O. L. Malta, C. de Mello Donegá, A. M. Simas, R. L. Longo, P. A. Santa-Cruz and E. F. da Silva Jr, *Coord. Chem. Rev.*, 2000, **196**, 165–195; (c) J.-C. G. Bünzli and C. Piguet, *Chem. Soc. Rev.*, 2005, **34**, 1048–1077; (d) N. M. Shavaleev, G. Accorsi, D. Virgili, D. R. Bell, T. Lazarides, G. Calogero, N. Armaroli and M. D. Ward, *Inorg. Chem.*, 2005, **44**, 61–72.

